



Original Article

Characterization and Antimicrobial Investigation of Synthesized Silver Nanoparticles from *Annona muricata* Leaf Extracts

Sunday Adewale Akintelu¹ and Aderonke Similoluwa Folorunso^{2*}

¹Department of Pure and Applied Chemistry, Ladoko Akintola University of Technology, Ogbomoso, Nigeria

²Department of Chemistry, Louisiana State University, Louisiana, USA

Abstract

Green synthesis is an ecological system for the production of eco-friendly and well characterized metallic nanoparticles using plants. In this research work, the synthesis of silver nanoparticles was from the extract of *Annona muricata* leaves. The characterization of silver nanoparticles was done with Fourier Transform Infrared spectroscopy (FTIR), UV-vis spectrometry and transmission electron microscope to determine functional groups, shape, size and morphology of synthesized nanoparticle. The anti-antimicrobial potency of the synthesized nanoparticle was investigated via well diffusion method. The UV spectrum of synthesized nanoparticle revealed absorbance at 435.00nm which confirmed the formation of silver nanoparticle. The FTIR analysis shows bands corresponding to -OH, C=O and -NH₂ nanoparticle are spherical shape of the functional group. The micrograph obtained from TEM analysis confirmed that the synthesized silver is spherical in shape. The antimicrobial investigation of the silver nanoparticles shows good antibacterial activity due to high zones of inhibition against test bacteria. This work revealed that the synthesized silver nanoparticles possess great antimicrobial potency.

Keywords: *Annona muricata*; Antimicrobial activity; Characterization; Silver nanoparticles

*Corresponding author: Aderonke Similoluwa Folorunso, Department of Chemistry, Louisiana State University, Louisiana, USA, Tel: +234 8136872649; E-mail: folorunadereksemi@gmail.com

Citation: Akintelu SA, Folorunso AS (2019) Characterization and Antimicrobial Investigation of Synthesized Silver Nanoparticles from *Annona muricata* Leaf Extracts. J Nanotechnol Nanomed Nanobiotechnol 6: 022.

Received: April 23, 2018; **Accepted:** May 02, 2018; **Published:** May 10, 2018

Copyright: © 2018 Akintelu SA and Folorunso AS. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.

Introduction

The usage of plants extracts for nanoparticles synthesis has various applications in life [1]. The reduction and elimination of the elegant process of upholding cell cultures associated with biological processes is an advantage of nanoparticle synthesis from plants. The use of plants in production of nanoparticles in large quantity can be aptly scaled up [2]. The multi-drug resistance of commercially available antibacterial drug against these pathogens calls for search of new bioactive compounds to eradicate this major health challenge [3].

Different nanomaterials like copper, nickel, gold, zinc and titanium has been reported [4,5]. Among all silver nanoparticles have demonstrated most effectiveness against bacteria there by showing good antimicrobial efficacy. Diverse approach such as the biological and chemical method for the synthesis of nanoparticles has been reported. Whoever, chemical methods have been reported to be very expensive and produce some toxic byproducts which are dangerous [6,7]. In quest to synthesis stable metal nanoparticles that are not expensive, safe, reliable and less toxic. Green synthesis is the application of chemistry in the scheming, developing and implementing of chemical yields to facilitate the eradication of hazardous substances that are dangerous to man and his environment [8]. Lately, the development of interest in the use of green chemistry approach in metal nanoparticles synthesis has greatly increased [9-12]. An innovative methods referred to as green/biosynthesis have been developed recently where extract of plants such as *Coriandrum sativum*, *Petroselinum crispum* [13,14]. *Murraya koenigii* and *Ocimum sanctum* were used as metal nanoparticles synthesis [10,15].

Among numerous plants *Annona muricata* leaves extract, was chosen for this study because of many pharmacological effects including anti-cancer, anti-inflammatory, anti-diabetic, antioxidant and hypotensive activities it possess [16,17]. The results obtained from the phytochemical screening of *Annona muricata* confirmed the presence of geranyl acetate, camphor, geraniol, coumarins and quercetin 3-glucuronide [18]. Also a lot of organic compounds such as xylopine, isolaureline, chlorogenic acid, chatechin, vomifoliol, roseoside, liliolide and epicatechin isolated from *Annona muricata* leaf has been reported to exhibit good inhibitory concentration against some bacterial has also been [18]. This study was aimed on the investigation of synthesized silver nanoparticles that is environmental friendly from the leaves of *Annona muricata* and evaluates their antimicrobial activity against some selected human pathogens.

Materials

Silver nitrate (AgNO₃; 99.9%, Sigma Aldrich, Germany). Leaves of *Annona muricata* were obtained from the premises of Obafemi Awolowo University, Ile-Ife, Nigeria. All chemicals used were of analytical grade.

Extraction procedure

Annona muricata leaf extract was prepared using green process technique; via standard procedure [19]. The leaves of *Annona muricata* collected was properly washed with distilled water so as to

remove foreign particles and dust available on the leaves surfaces. About Twenty (20) grams of leaves of *Annona muricata* were pulverized and boiled in 100 mL distilled water with 250 mL flask for 30 minutes. The extract was filtered. The removal of heavy molecular weight constituents in the extract was removed by centrifuging at 7500 rpm. The pH of the *Annona muricata* extract was 7.5 and kept at 4°C for supplementary experimental analysis. Extract of about 5 mL was added to 45 ml of 0.01M AgNO_3 solution and was left to react at room temperature. The colour of the solution changes from transparent yellow to dark brown and the intensity of the colour also increase with time which signifies the formation of silver nanoparticle.

Characterization of synthesized nanoparticles

Shimadzu UV-1800 model of UV-vis spectrometer operated on a resolution of 1 nm with absorbance in the region 250 and 900 nm wavelength was used for the examination of the reduction mechanism of silver ion. The (FTIR) spectrum was used to determine the functional groups in the *Annona muricata* extract and the nanoparticle produced. FTIR spectra were measured by Shimadzu spectrometer in the wavelength of 500-4000 cm^{-1} . The particle size and surface morphology of silver nanoparticle synthesized was measured with transmission electron microscopy.

Antimicrobial activity of synthesized nanoparticles by well diffusion method

The antimicrobial activity of the synthesized nanoparticles was tested against some bacterial and fungal clinical pathogens by agar disc diffusion method. The cultures were swab in pre-sterilized Muller Hinton agar plates under aseptic condition was used. The Plates were permitted to stay for 10 minutes to absorb the cultures. Then three 8mm wells were punched into the Muller Hinton agar plates to examine the antimicrobial activity of the synthesized nanoparticles. 20 μl of each test sample at different concentrations (50,75,100 $\mu\text{g/ml}$) was transferred into each of the punched wells and closed using 0.8% molten agar. Tetracycline and Chloramphenicol were used as control for bacteria and fungi test pathogen respectively. The incubation of the plates was done at 37°C for 22 hours. The inhibition zones of test pathogens were measured after incubation period.

Results and Discussion

UV-Vis spectroscopy

The noticeable peaks at 435nm showed on the UV-Vis spectra illustrated in figure 1 correspond to silver nanoparticles surface plasmon resonance. This suggested that the reduction Ag^+ ions have been ascertained. Absorbance at 0.556 around 431.6nm wavelength has been reported for silver [20]. The maximum absorbance detected at 435.00nm on the spectrum of synthesized silver nanoparticle was in the range earlier reported for biosynthesized silver nanoparticles, 350-550nm [21-24].

FTIR analysis

The FTIR spectrum of the extracts shows number of absorption peaks, as showed in figures 2a and 2b. Strong absorption bands at 3431 to 3433 cm^{-1} are a signal of bonded -OH of alcohol or possibly -NH of amine. The absorption peaks at 2924 cm^{-1} could be allotted to alkane stretching vibrations and that at 1664 cm^{-1} can be allotted to tertiary amides C=O stretching [25]. Reported that bands in the range

of 1400-1600, 1640-1690, 2850-3000 and 1000-1300 cm^{-1} are groups assisting reduction of silver nanoparticle [26]. The FTIR analysis confirmed (-OH) and amine (-N-H) as functional groups accountable for the reduction of Ag^+ ions to Ag^0 .

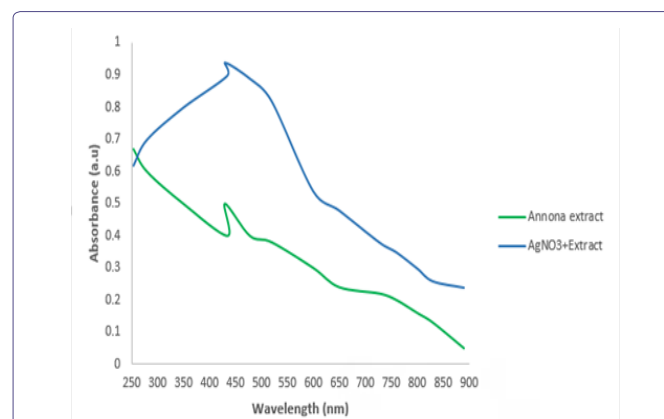


Figure 1: UV-visible absorption spectrum of silver nanoparticle produced.

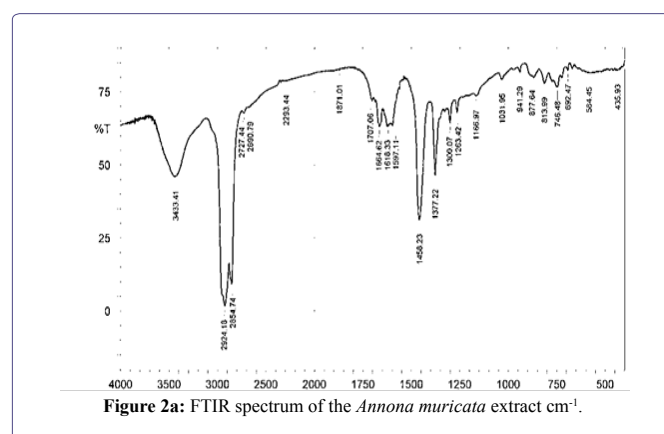


Figure 2a: FTIR spectrum of the *Annona muricata* extract cm^{-1} .

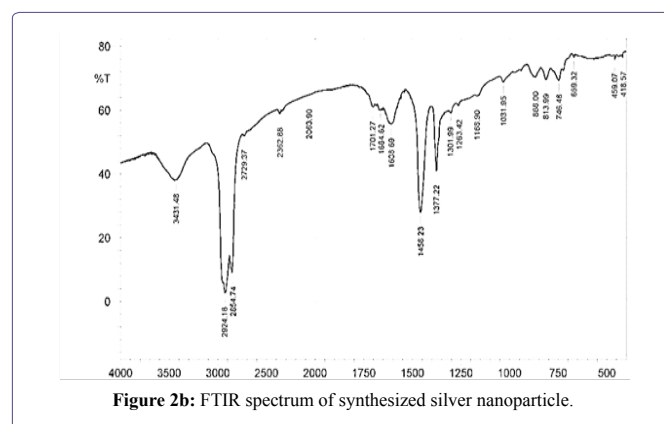


Figure 2b: FTIR spectrum of synthesized silver nanoparticle.

Transmission Electron Microscopic (TEM) analysis

The morphology and particle size of nanoparticles synthesized from *Annona muricata* extract was scanned with transmission electron

microscopic. The TEM micrograph showed in figure 3 indicated mono-dispersed silver nanoparticles with spherical shape. The result obtained from the TEM analysis is consistent with previous findings of [27]. The TEM micrograph of synthesized nanoparticles at 100nm magnification indicates an average size ranging from 22-28nm and was spherical in shape.

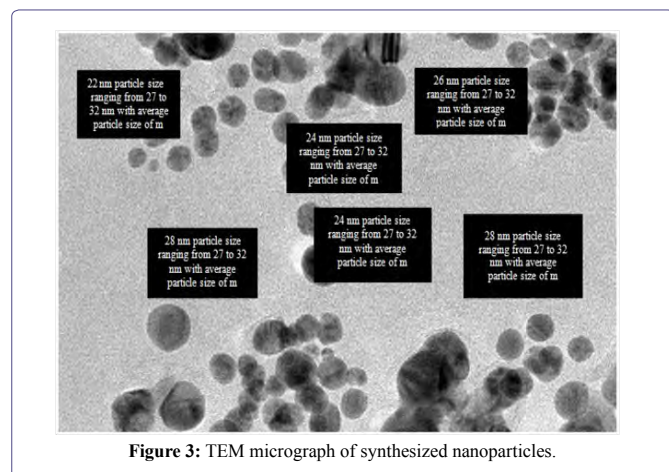


Figure 3: TEM micrograph of synthesized nanoparticles.

Antimicrobial analysis of synthesized silver nanoparticle

The zones of inhibition of the synthesized nanoparticles against the selected fungi (*Aspergillus flavus*, *Penicillium camemeri* and *Candida albican*) at concentrations of 50, 75 and 100µg are showed in table 1, figures 4 and 5: The highest zone of inhibition against the test fungi was observed at the 100µg of silver nanoparticles against *Candida albican* while the least zone of inhibition was detected at concentration of 50µg of silver nanoparticles against *Penicillium camemeri*. The higher the concentration of silver nanoparticle against the test fungi the higher the zones of inhibition observed. The silver nanoparticles especially at high concentration compete moderately with the control (Chloramphenicol) when compared.

Bacterial test pathogens	Inhibition zone of silver nanoparticle(mm)			
	Concentration (µg)			Tetracycline
	50	75	100	
<i>Pseudomonas aeruginosa</i>	12	17	22	28
<i>Klebsiella pneumonia</i>	10	15	20	23
<i>Bacillus subtilis</i>	13	16	18	10
Fungi test pathogens	Concentration (µg)			Chloramphenicol
	50	75	100	
	<i>Aspergillus flavus</i>	12	13	15
<i>Penicillium camemeri</i>	5	15	17	20
<i>Candida albican</i>	13	17	19	23

Table 1: Zones of inhibition of silver nanoparticles against test bacteria and fungi.

The synthesized silver nanoparticles showed high inhibition zones against selected bacterial namely; *Pseudomonas aeruginosa*, *Klebsiella pneumonia* and *Bacillus subtilis* especially at 100µg where the Inhibition zones are 22, 20 and 18mm as showed in table 1. Lowest inhibition zone was observed when 50µg of silver nanoparticle was used against *Klebsiella pneumonia* while highest inhibition zone was

observed when 100µg of silver nanoparticle was used against *Pseudomonas aeruginosa*. The potency of the synthesized nanoparticle increases as concentrations of synthesized nanoparticles used against the test bacterial increase due to the observed zones of inhibition. The antimicrobial assay used in this study shows a better inhibition zones when compared with inhibition zones obtained from the antimicrobial assay used by on *Juglan regia* extract and that used by on some novel antibiotics [29,30]. The inhibition zones in this study were higher than that obtained from the study of at concentration of 50, 75 and 100µg [28]. The synthesized silver nanoparticles compete better than the control (tetracycline) at all concentration against *Bacillus subtilis*. This suggests that silver nanoparticles synthesized using *Annona muricata* can inhibit both gram positive and gram negative bacteria. This is evidence that the synthesized silver nanoparticle exhibit good antibacterial activity.



Figure 4: Antibacterial activity of synthesized silver nanoparticles from *Annona muricata* leaf.



Figure 5: Antifungal activity of synthesized silver nanoparticles from *Annona muricata* leaf.

Conclusion

The synthesized silver nanoparticle from *Annona muricata* leaf was fairly uniform in size, shape and spherical in shape. The FTIR spectrum shows absorption bands corresponding to -OH, -NH and C=C functional groups. The synthesized silver nanoparticles from *Annona muricata* leaf in this study was eco-friendly, cost effective and also possess good antibacterial and antifungal activities.

References

1. Logeswari P, Silambarasan S, Abraham J (2013) Ecofriendly synthesis of silver nanoparticles from commercially available plant powders and their antibacterial properties. *Scientia Iranica* 20: 1049-1054.
2. Gajbhiye M, Kesharwani J, Ingle A, Gade A, Rai M (2009) Fungus-mediated synthesis of silver nanoparticles and their activity against pathogenic fungi in combination with fluconazole. *Nanomedicine* 5: 382-386.
3. Bhatt P, Negi PS (2012) Antioxidant and antibacterial activities in the leaf extracts of Indian Borage (*Plectranthus amboinicus*). *Food and Nutrition Sciences* 3: 146-152.
4. Gu H, Ho PL, Tong E, Wang L, Xu B (2003) Presenting vancomycin on nanoparticles to enhance antimicrobial activities. *Nano Letter* 3: 1261-1263.
5. Schabes-Retchkiman P, Canizal G, Herrera-Becerra R, Cangas CZ, Liu HB, et al. (2006) Biosynthesis and characterization of Ti/Ni bimetallic nanoparticles. *Optical Materials* 29: 95-99.
6. Phanjom P, Ahmed G (2015) Biosynthesis of silver nanoparticles by *Aspergillus oryzae* (MTCC No. 1846) and its characterizations. *Nanoscience and Nanotechnology* 5: 14-21.
7. Vinod VT, Saravanan P, Sreedhar B, Devi DK, Sashidhar RB (2011) A facile synthesis and characterization of Ag, Au and Pt nanoparticles using a natural hydrocolloid gum kondagogu (*Cochlospermum gossypium*). *Colloids Surf B Biointerfaces* 83: 291-298.
8. Kumar SH, Prasad CH, Venkateswarlu S, Venkateswarlu P, Jyothi NVV (2015) Green Synthesis of Silver Nanoparticles Using Aqueous Solution of *Syzygium cumini* Flowering Extract and its Antimicrobial Activity. *Indian Journal of Advances in Chemical Science* 3: 299-303.
9. Geethalakshmi R, Sarada DVL (2010) Synthesis of plant-mediated silver nanoparticles using *Trianthema decandra* extract and evaluation of their anti microbial activities. *International Journal Engineering Science and Technology* 2: 970-975.
10. Christensen L, Vivekanandhan S, Misra M, Mohanty AK (2011) Biosynthesis Of Silver Nanoparticles Using *Murraya koenigii* (Curry Leaf): An Investigation On The Effect Of Broth Concentration In Reduction Mechanism And Particle Size. *Advance Material Letter* 2: 429-434.
11. Arokiyaraj S, Arasu MV, Vincent S, Prakash NU, Choi SH, et al. (2014) Rapid green synthesis of silver nanoparticles from *Chrysanthemum indicum* L and its antibacterial and cytotoxic effects: An *in vitro* study. *Int J Nanomedicine* 9: 379-388.
12. Gandhi N, Sirisha D, Sharma VC (2014) Microwave-Mediated Green Synthesis of Silver Nanoparticles Using *Ficus elastica* Leaf Extract and Application in Air Pollution Controlling Studies. *International Journal of Engineering Research and Applications* 4: 61.
13. Singhal G, Bhavesh R, Kasariya K, Sharma AR, Singh RP (2011) Biosynthesis of silver nanoparticles using *Ocimum sanctum* (Tulsi) leaf extract and screening its antimicrobial activity. *Journal of Nanoparticle Research* 13: 2981-2988.
14. Roy K, Sarkar CK, Ghosh CK (2015) Plant-mediated synthesis of silver nanoparticles using parsley (*Petroselinum crispum*) leaf extract: spectral analysis of the particles and antibacterial study. *Applied Nanoscience* 5: 945-951.
15. Sathyavathi R, Krishna MB, Rao SV, Saritha R, Rao DN (2010) Biosynthesis of silver nanoparticles using *Coriandrum sativum* leaf extract and their application in nonlinear optics. *Advance Science Letter* 3: 138-143.
16. Muthu S, Durairaj B (2015) Evaluation of antioxidant and free radical scavenging activity of *Annona muricata*. *European Journal of Experimental Biology* 5: 39-45.
17. de Sousa OV, Vieira GD, de Jesus R G de Pinho J, Yamamoto CH, Alves MS (2010) Antinociceptive and Anti-Inflammatory Activities of the Ethanol Extract of *Annona muricata* L. Leaves in Animal Models. *Int J Mol Sci* 11: 2067-2078.
18. Patel S, Patel JK (2016) A review on a miracle fruits of *Annona muricata*. *Journal of Pharmacognosy and Phytochemistry* 5: 137-148.
19. Espenti CS, Rao KSVK, Rao KM (2016) Bio-synthesis and characterization of silver nanoparticles using *Terminalia chebula* leaf extract and evaluation of its antimicrobial potential. *Material Letter* 174: 129-133.
20. El-Nour KMMA, Eftaiha A, Al-Warthan A, Ammar RAA (2010) Synthesis and applications of silver nanoparticles. *Arabian Journal Chemistry* 3: 135-140.
21. Bose D, Chatterjee S (2016) Biogenic synthesis of silver nanoparticles using guava (*Psidium guajava*) leaf extract and its antibacterial activity against *Pseudomonas aeruginosa*. *Applied Nanoscience* 6: 895-901.
22. Namratha N, Monica PV (2013) Synthesis of silver nanoparticles using *Azadirachta indica* (Neem) extract and usage in water purification. *Asian Journal Pharmaceutical Technology* 3: 170-174.
23. Agrawal P, Mehta K, Vashisth P, Sudarshan, Bhat P, et al. (2014) Green Synthesis of Silver Nanoparticles and Their Application in Dental Filling Material. *International Journal of Innovative Science Engineering and Technology* 3: 13038-13052.
24. Gavhane AJ, Padmanabhan P, Kamble SP, Jangle SN (2012) Synthesis of silver nanoparticles using extract of Neem leaf and Triphala and evaluation of their antimicrobial activities. *Int J Pharm Bio Sci* 3: 88-100.
25. Khan MZH, Tareq FK, Hossen MA, Roki MNAM (2018) Green Synthesis and Characterization of Silver Nanoparticles Using *Coriandrum sativum* Leaf Extract. *Journal of Engineering Science and Technology* 1: 158-166.
26. Sapna GY, Sudeep HP, Pratima P, Vineetha N, Shahida K, et al. (2018) Green synthesis of silver nanoparticles from plant sources and evaluation of their antimicrobial activity. National Conference on 'Advanced Analytical Tools for Materials Characterization 4: 133-139.
27. Kumar S, Daimary RM, Swargiary M, Brahma A, Kumar S, et al. (2013) Biosynthesis of silver nanoparticles using *Premna herbacea* leaf extract and evaluation of its antimicrobial activity against bacteria causing dysentery. *International Journal of Pharma and Bio Sciences* 4: 378-384.
28. Niveditha K, Sukirtha TH (2018) Green Synthesis, Characterization and Antimicrobial Activity of Silver Nanoparticles from *Plectranthus amboinicus* Plant Extracts. *Indian Journal of Medical Research and Pharmaceutical Sciences* 5: 41-51.
29. Iqbal J, Siddiqui R, Kazmi SU, Khan NA (2013) A Simple Assay to Screen Antimicrobial Compounds Potentiating the Activity of Current Antibiotics. *BioMed Research International* Pg no: 1-4.
30. Butler MS, Buss AD (2006) Natural products--the future scaffolds for novel antibiotics? *Biochem Pharmacol* 71: 919-929.



Journal of Anesthesia & Clinical Care
Journal of Addiction & Addictive Disorders
Advances in Microbiology Research
Advances in Industrial Biotechnology
Journal of Agronomy & Agricultural Science
Journal of AIDS Clinical Research & STDs
Journal of Alcoholism, Drug Abuse & Substance Dependence
Journal of Allergy Disorders & Therapy
Journal of Alternative, Complementary & Integrative Medicine
Journal of Alzheimer's & Neurodegenerative Diseases
Journal of Angiology & Vascular Surgery
Journal of Animal Research & Veterinary Science
Archives of Zoological Studies
Archives of Urology
Journal of Atmospheric & Earth-Sciences
Journal of Aquaculture & Fisheries
Journal of Biotech Research & Biochemistry
Journal of Brain & Neuroscience Research
Journal of Cancer Biology & Treatment
Journal of Cardiology & Neurocardiovascular Diseases
Journal of Cell Biology & Cell Metabolism
Journal of Clinical Dermatology & Therapy
Journal of Clinical Immunology & Immunotherapy
Journal of Clinical Studies & Medical Case Reports
Journal of Community Medicine & Public Health Care
Current Trends: Medical & Biological Engineering
Journal of Cytology & Tissue Biology
Journal of Dentistry: Oral Health & Cosmesis
Journal of Diabetes & Metabolic Disorders
Journal of Dairy Research & Technology
Journal of Emergency Medicine Trauma & Surgical Care
Journal of Environmental Science: Current Research
Journal of Food Science & Nutrition
Journal of Forensic, Legal & Investigative Sciences
Journal of Gastroenterology & Hepatology Research
Journal of Gerontology & Geriatric Medicine
Journal of Genetics & Genomic Sciences
Journal of Hematology, Blood Transfusion & Disorders
Journal of Human Endocrinology
Journal of Hospice & Palliative Medical Care
Journal of Internal Medicine & Primary Healthcare
Journal of Infectious & Non Infectious Diseases
Journal of Light & Laser: Current Trends
Journal of Modern Chemical Sciences
Journal of Medicine: Study & Research
Journal of Nanotechnology: Nanomedicine & Nanobiotechnology
Journal of Neonatology & Clinical Pediatrics
Journal of Nephrology & Renal Therapy
Journal of Non Invasive Vascular Investigation
Journal of Nuclear Medicine, Radiology & Radiation Therapy
Journal of Obesity & Weight Loss
Journal of Orthopedic Research & Physiotherapy
Journal of Otolaryngology, Head & Neck Surgery
Journal of Protein Research & Bioinformatics
Journal of Pathology Clinical & Medical Research
Journal of Pharmacology, Pharmaceutics & Pharmacovigilance
Journal of Physical Medicine, Rehabilitation & Disabilities
Journal of Plant Science: Current Research
Journal of Psychiatry, Depression & Anxiety
Journal of Pulmonary Medicine & Respiratory Research
Journal of Practical & Professional Nursing
Journal of Reproductive Medicine, Gynaecology & Obstetrics
Journal of Stem Cells Research, Development & Therapy
Journal of Surgery: Current Trends & Innovations
Journal of Toxicology: Current Research
Journal of Translational Science and Research
Trends in Anatomy & Physiology
Journal of Vaccines Research & Vaccination
Journal of Virology & Antivirals

Submit Your Manuscript: <http://www.heraldopenaccess.us/Online-Submission.php>